

Abrasive Properties of Modified Oxides for Finish Polishing of Steel

**Абразивные свойства
модифицированных оксидов для
финишного полирования стали**

L. F. Koroleva

*Institute of Engineering Science, Ural Branch of the
Russian Academy of Sciences,
34 Komsomolskaya St., Ekaterinburg, Russian
Federation*

The study of modified chromium and aluminum oxides, demonstrates that finish polishing by modified hydroxocomplexes based on a solid solution of iron and aluminum oxides provide a surface nanoroughness of 0.02 to 0.005 μm for the hardened ShKh15 steel (American Standard AISI 52100).

At the same time, among the most effective abrasive powders there are transition-metal and rare-earth oxides with medium hardness (5–7 on the Mohs Scale): CeO_2 , ZrO_2 , Cr_2O_3 , Al_2O_3 , Fe_2O_3 . They are, however, not always capable of ensuring a sufficient abrasion rate or surface roughness class. Solid solutions of oxides, e.g. chromia and alumina, offer a higher abrasive performance. Modification of chromium oxide with the formation of solid solutions with REE and calcium results in increased polishability while providing a surface roughness of less than $R_a = 0.08 \mu\text{m}$. Aluminum and iron oxides prepared from hydroxycarbonate complexes are known to possess high polishing performance for final polishing of the quenched ShKh15 steel with austenitic-martensitic structure and to provide a nanorough surface owing to their high tribochemical activity .

One attractive approach to the preparation of nanoparticles is chemical modification of layered structures through the formation of $M_{1-x}^{2+}M_x^3(\text{OH})_2 (X^{n-})_{x/n} \cdot m\text{H}_2\text{O}$.

Selecting and developing new abrasive materials should be based on the knowledge of the processes of polishing.

The abrasive properties of samples in the polishing process were assessed by standard procedures of measuring the variation of polishability and surface roughness (Ra), with a Wyko NT1100 optical profiler, to find the arithmetic mean of the roughness profile with a sampling length of 0.08 mm. The source samples were made of hardened steel with an austenitic-martensitic structure, the initial value of Ra being 0.2 to 0.3 μm. The process performance (polishability) of polishing was evaluated by the formula

$$P = \Delta M / (S \cdot t),$$

where ΔM is a change in the mass of the samples during polishing, mg; S is the size of the polished surface, cm²; t is the duration of polishing, min.

Surface roughness, Ra, is the arithmetic mean of the absolute value deviations within the profile length, and it is determined as follows:


$$R_a = 1/n \sum |y_i|$$

Modification of chromium oxide with the formation of solid solutions with rare-earth elements and calcium has the effect of enhancing the polishing ability while providing a surface roughness of 0.07 to 0.08 μm. The use of chromium oxide modified by CaO and ZrO₂ improves the quality of polishing and increases the output of high-precision products made of the hardened ShKh15 steel by 80-82%.

The abrasive material produced by thermal treatment of ammonium hydroxycarbonate of aluminum and iron has high abrasive properties. The total reaction of hydroxycarbonate deposition can be presented as follows:



As a result of thermal influence on ammonium hydroxycarbonate, solid solutions on the basis of hematite and corundum are formed



To obtain the lowest surface roughness $Ra = 0.002 \mu\text{m}$, solid solution containing iron oxide in the range of 0.156 to 0.125 mol% must be used. This is due to the formation of solid solution phases based on corundum and hematite with nanosized particles. Extreme polishing ability is observed for samples based on the solid solution of aluminum and iron oxides (Fig. 1).

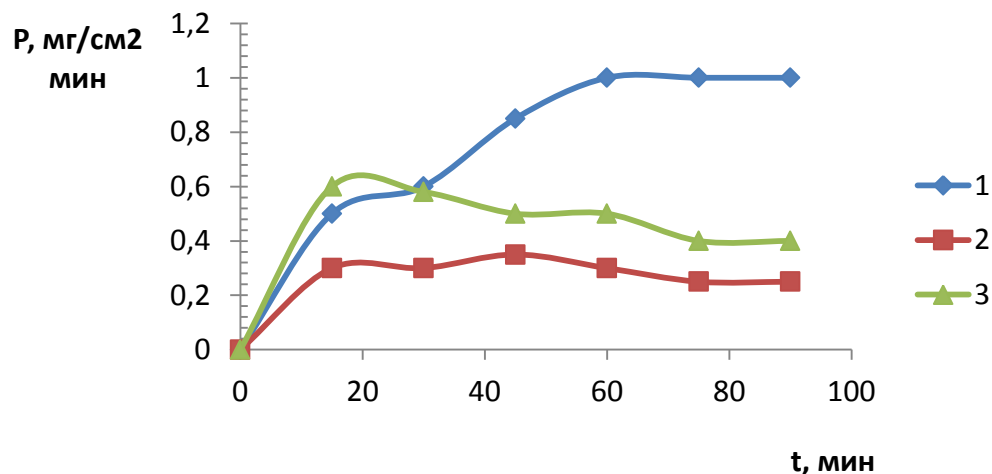


FIGURE 1. Abrasion ability P as a function of polishing time (Steel ShKh15): solid solution based on an aluminum-iron oxide (1), chromium oxide modified by CaO and ZrO_2 (2) and boron carbide (3)

The lowest roughness is demonstrated by the samples made of steel treated with a solid solution of aluminum and iron oxides ($R_a = 0.002$ to $0.005 \mu\text{m}$). Polishing with boron carbide fails to provide surface nanoroughness. The data on deposition and the results of electron microscopy have shown that the samples based on the solid solution of aluminum-iron oxide (Fe_2O_3 0.12 to 0.156 mol%) contain nanoparticles with sizes up to 10 nm in the range of 4-5%.

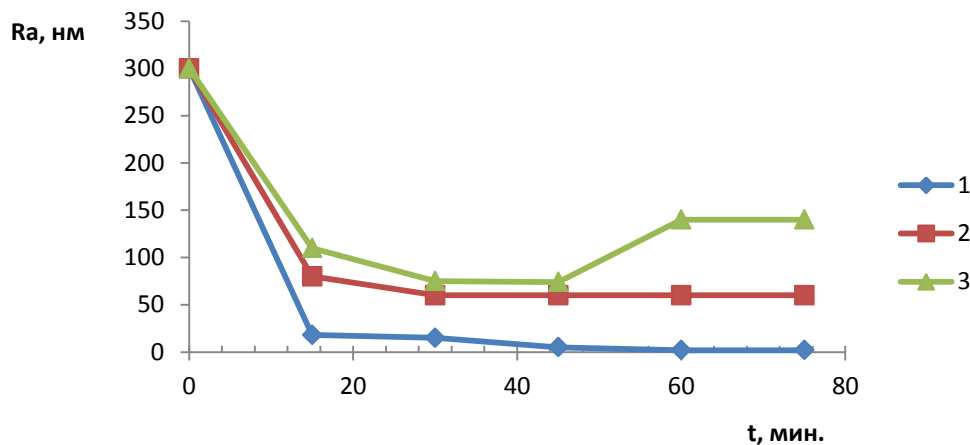


FIGURE 2. Surface roughness R_a as a function of polishing time: solid solution of aluminum-iron oxide (1); chromium oxide modified by CaO and ZrO_2 (2); boron carbide (3)

CONCLUSION

The study has revealed that the lowest surface roughness ($R_a = 0.005$ to $0.002 \mu\text{m}$) of the finish-polished ShKh15 steel (American Standard AISI 52100) is obtained with the abrasive material based on a solid solution of aluminum-iron oxide. Polishing by currently used boron carbide and modified chromium oxide fails to provide a nanorough surface.

ACKNOWLEDGMENT

The equipment of the Plastometriya collective use center affiliated to the Institute of Engineering Science, Russian Academy of Sciences (Ural Branch), was used in the experiment.